

Breakdown of three-dimensional Dirac semimetal state in pressurized Cd₃As₂

Shan Zhang,¹ Qi Wu,¹ Leslie Schoop,² Mazhar N. Ali,² Youguo Shi,¹ Ni Ni,³ Quinn Gibson,² Shang Jiang,³ Vladimir Sidorov,⁴ Wei Yi,¹ Jing Guo,¹ Yazhou Zhou,¹ Desheng Wu,¹ Peiwen Gao,¹ Dachun Gu,¹ Chao Zhang,¹ Sheng Jiang,⁵ Ke Yang,⁵ Aiguo Li,⁵ Yanchun Li,⁶ Xiaodong Li,⁶ Jing Liu,⁶ Xi Dai,^{1,7} Zhong Fang,^{1,7} Robert J. Cava,^{2,*} Liling Sun,^{1,7,†} and Zhongxian Zhao^{1,7,‡}

¹*Institute of Physics and Beijing National Laboratory for Condensed Matter Physics, Chinese Academy of Sciences, Beijing 100190, China*

²*Department of Chemistry, Princeton University, Princeton, New Jersey 08544, USA*

³*Department of Physics and Astronomy, UCLA, Los Angeles, California, 90095, USA*

⁴*Institute for High Pressure Physics, Russian Academy of Sciences, 142190 Troitsk, Moscow, Russia*

⁵*Shanghai Synchrotron Radiation Facilities, Shanghai Institute of Applied Physics, Chinese Academy of Sciences, Shanghai 201204, China*

⁶*Institute of High Energy Physics, Chinese Academy of Sciences, Beijing 100049, China*

⁷*Collaborative Innovation Center of Quantum Matter, Beijing, 100190, China*

(Received 4 January 2015; revised manuscript received 5 April 2015; published 27 April 2015)

We report an observation of a pressure-induced breakdown of the three-dimensional Dirac semimetal (3D-DSM) state in Cd₃As₂, evidenced by a series of *in situ* high-pressure synchrotron x-ray diffraction and single-crystal transport measurements. We find that Cd₃As₂ undergoes a structural phase transition from a metallic tetragonal phase in space group $I4_1/acd$ to a semiconducting monoclinic phase in space group $P2_1/c$ at critical pressure 2.57 GPa; above this pressure, an activation energy gap appears, accompanied by distinct switches in Hall resistivity slope and electron mobility. These changes of crystal symmetry and corresponding transport properties manifest the breakdown of the 3DDSM state in pressurized Cd₃As₂.

DOI: [10.1103/PhysRevB.91.165133](https://doi.org/10.1103/PhysRevB.91.165133)

PACS number(s): 71.55.Ak, 74.62.Fj, 71.30.+h

Three-dimensional Dirac semimetals (3DDSMs) are a new class of materials having nontrivial topology in their electronic states, featured by 3D Dirac points in the bulk and Fermi arcs on the surfaces [1–4]. These intriguing states predicted by theorists have been identified experimentally in real materials. Cd₃As₂ and Na₃Bi are the materials with such a unique electronic structure [5–11]. Their conduction and valence bands contact at 3D Dirac points in momentum space where Dirac fermions disperse linearly along all momentum directions, resulting in the band gap closing in the bulk. Consistent within this picture, Cd₃As₂ has high mobilities for electrons in bulk crystals [12–19], so that it is expected to be a promising candidate in device applications [20,21].

Similar to topological insulators, the 3DDSM state is protected by either time reversal symmetry (TRS) or crystal rotational symmetry (CRS) along the z axis [1,2,22–27]. On the breaking of TRS or CRS, the 3DDSM state may be tuned into a variety of quantum states with interesting physical properties [27–32]. The tuning effect may be realized by either applying pressure or chemical doping. Of these two ways, pressure is an ideal method for finely tuning a system from one state to another without introducing chemical complexity; therefore the behavior of 3D-DSMs under pressure is of current research interest. In this study, we demonstrate that the pressure-induced alternation of CRS leads to the breakdown of the 3DDSM state in single-crystal Cd₃As₂, and we show how the transport properties change correspondingly.

High-quality single crystals of Cd₃As₂ were grown by the flux method, as described in Ref. [33]. Pressure was generated by a diamond anvil cell (DAC) with two opposing anvils sitting

on a Be-Cu supporting plate. Diamond anvils with 500- and 300- μ m flats were used for this study. A nonmagnetic rhenium gasket with 200- and 100- μ m-diameter holes was used for different runs of the high-pressure studies. The four-probe method was applied in the (112) cleavage plane of a single crystal of Cd₃As₂ for all high-pressure transport measurements. To keep the sample in a quasihydrostatic pressure environment, NaCl powder was employed as the pressure medium for the high-pressure resistance and Hall measurements. The high-pressure heat capacity (C_{ac}) of Cd₃As₂ was derived from *ac* calorimetry [34,35]. High-pressure x-ray diffraction (XRD) experiments were performed at beam line 15U at the Shanghai Synchrotron Radiation Facility and at beam line 4W2 at the Beijing Synchrotron Radiation Facility. Diamonds with low birefringence were selected for the experiments. A monochromatic x-ray beam with a wavelength of 0.6199 Å was adopted for all measurements. Pressure was determined by the ruby fluorescence method [36].

We first performed high-pressure powder x-ray diffraction measurements to detect the structural stability of Cd₃As₂ under pressure, because the 3DDSM state is protected by the CRS along the z axis [1,2,27,31]. As shown in Fig. 1(a), Cd₃As₂ has a tetragonal unit cell in the tetragonal $I4_1/acd$ space group at ambient pressure, as reported in Ref. [33]. Applying pressure up to 2.42 GPa, no new peaks appear over the range of 2θ angles studied. Instead, pressure shifts each Bragg peak to a higher angle, reflecting a continuous reduction of the d spacing in the tetragonal (T) phase. By pressures of \sim 3.78 GPa and above, a set of new diffraction peaks is clearly visible, demonstrating that the ambient-pressure crystal symmetry is destroyed and a different crystal structure is present at high pressures. High-pressure resistance measurements indicate that the precise critical pressure for the phase transition is 2.57 GPa [Fig. 1(b)]. To trace the stability of the two phases (T phase and new high-pressure phase) as temperature changes,

*rcava@Princeton.edu

†llsun@iphy.ac.cn

‡zhxzhao@iphy.ac.cn

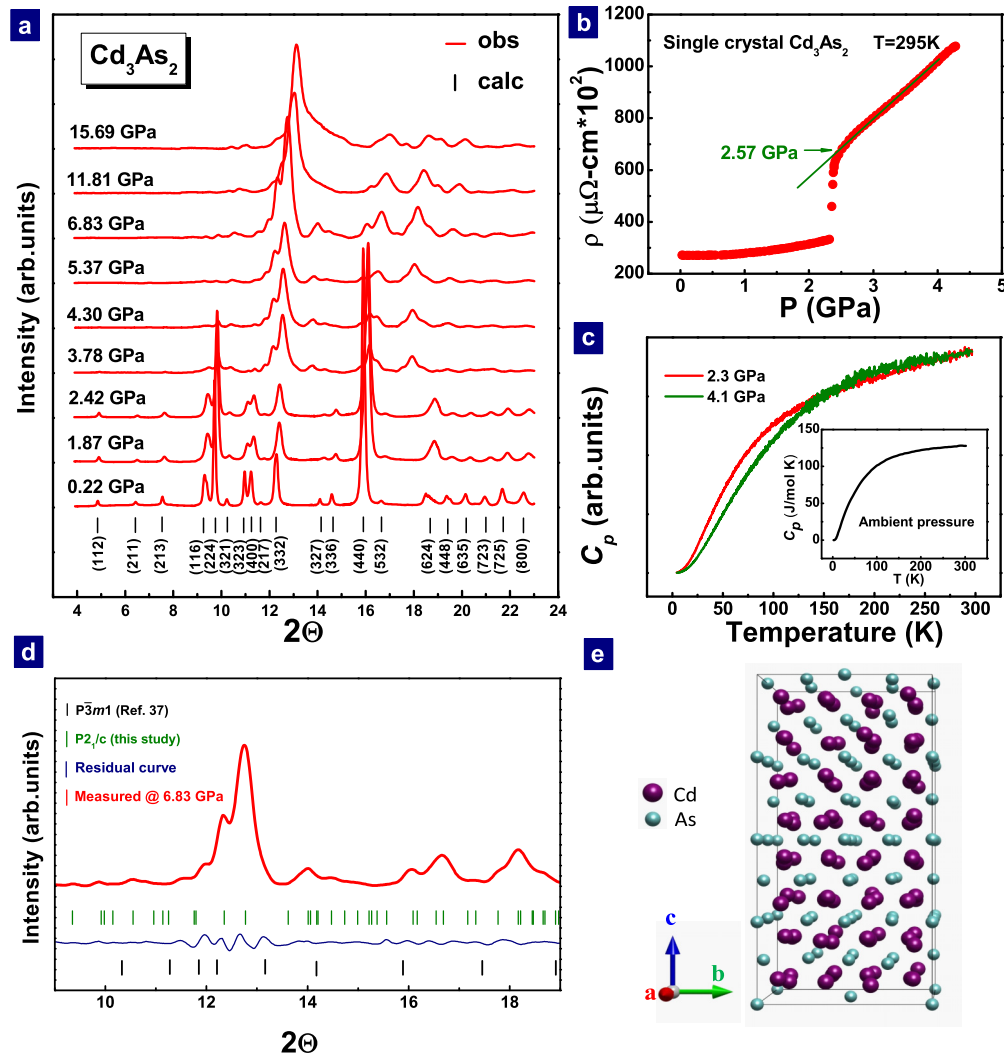


FIG. 1. (Color online) (a) X-ray powder diffraction patterns of Cd_3As_2 at various pressures at room temperature. The data below 2.42 GPa can be indexed well as the tetragonal (T) phase in space group $I4_1/acd$ (as indicated by short black lines), while on increasing pressure to 3.78 GPa and above, the data show a set of new peaks, indicating a phase transition from the T phase to the high-pressure phase. (b) Pressure dependence of electrical resistance for single-crystal Cd_3As_2 . The onset pressure of the transition is located at 2.57 GPa. (c) Temperature dependence of the heat capacity of a single crystal of Cd_3As_2 at 2.3 and 4.1 GPa. The heat capacity measured at different pressures decreases smoothly with decreasing temperature, demonstrating that no structural phase transitions occur in the temperature range of 4–295 K. The inset shows the heat capacity as a function of temperature measured at ambient pressure, which is in good agreement with the results of Ref. [42]. (d) Powder XRD data for Cd_3As_2 measured at 6.83 GPa, showing that the high-pressure phase is the monoclinic one in space group $P2_1/c$. (e) Three-dimensional structure of monoclinic phase.

we performed high-pressure specific heat measurements at 2.3 and 4.1 GPa, respectively. We find that, once formed, both the T phase and the new high-pressure phase are stable under the temperatures ranging from 300 to 4 K [Fig. 1(c)].

Years ago, the pressure-induced structural phase transition in Cd_3As_2 was studied by x-ray diffraction camera (XRDC) [37] and differential thermal analysis (DTA) [38], respectively. The XRDC measurements showed that Cd_3As_2 transforms into a trigonal structure in space group $P\bar{3}m1$ at pressures near 2.5 GPa [37], while the DTA results proposed that Cd_3As_2 undergoes a crystal phase transition at ~ 1.7 GPa but no XRD data are provided [38]. However, as shown in Fig. 1(d), most of our x-ray diffraction peaks of the pressurized Cd_3As_2 phase (the peak positions are indicated by short green lines)

do not come close to the peak positions calculated from the proposed trigonal symmetry cell (as indicated by short black lines) [37]. We thus do the refinements for the high-pressure x-ray diffraction data and find that the high-pressure phase is monoclinic (M) in space group $P2_1/c$ [Figs. 1(d) and 1(e)]. The pressure dependence of lattice parameters in the T and M phases can be found in Fig. S1 (Supplemental Material [39]). The obtained results indicate that pressure induces a change of CRS from a space group based on fourfold rotational symmetry to the one based on twofold rotational symmetry.

High-pressure transport measurements reveal details of the property changes before and after the crystal structure phase transition. Figure 2 shows the temperature-dependent resistance at different pressures. As can be seen, pressure

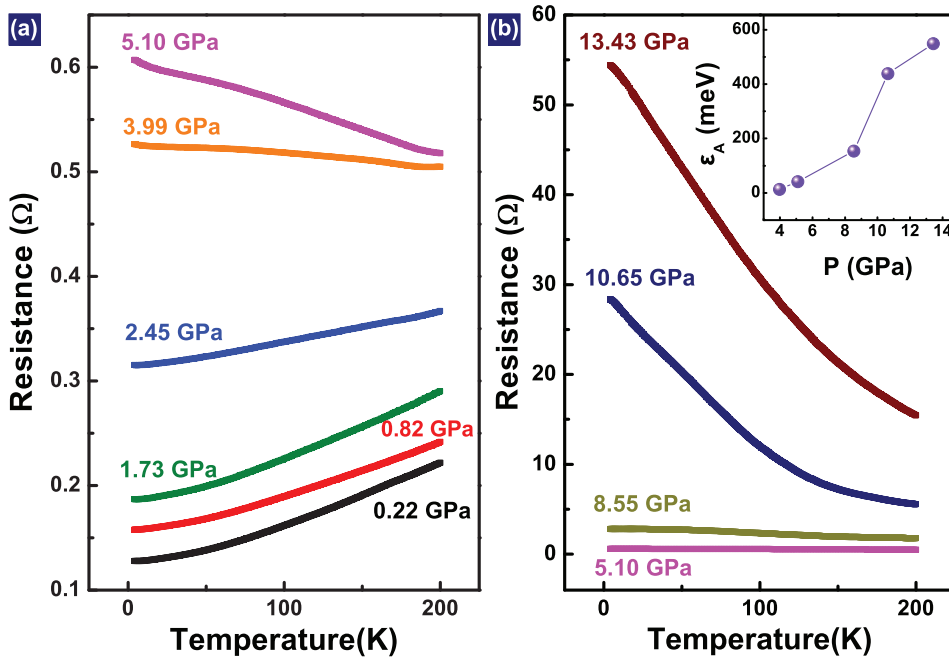


FIG. 2. (Color online) Temperature dependence of electrical resistance for single-crystal Cd_3As_2 at different pressures. The inset of Fig. 2(b) displays the activation energy gap ϵ_A as a function of pressure.

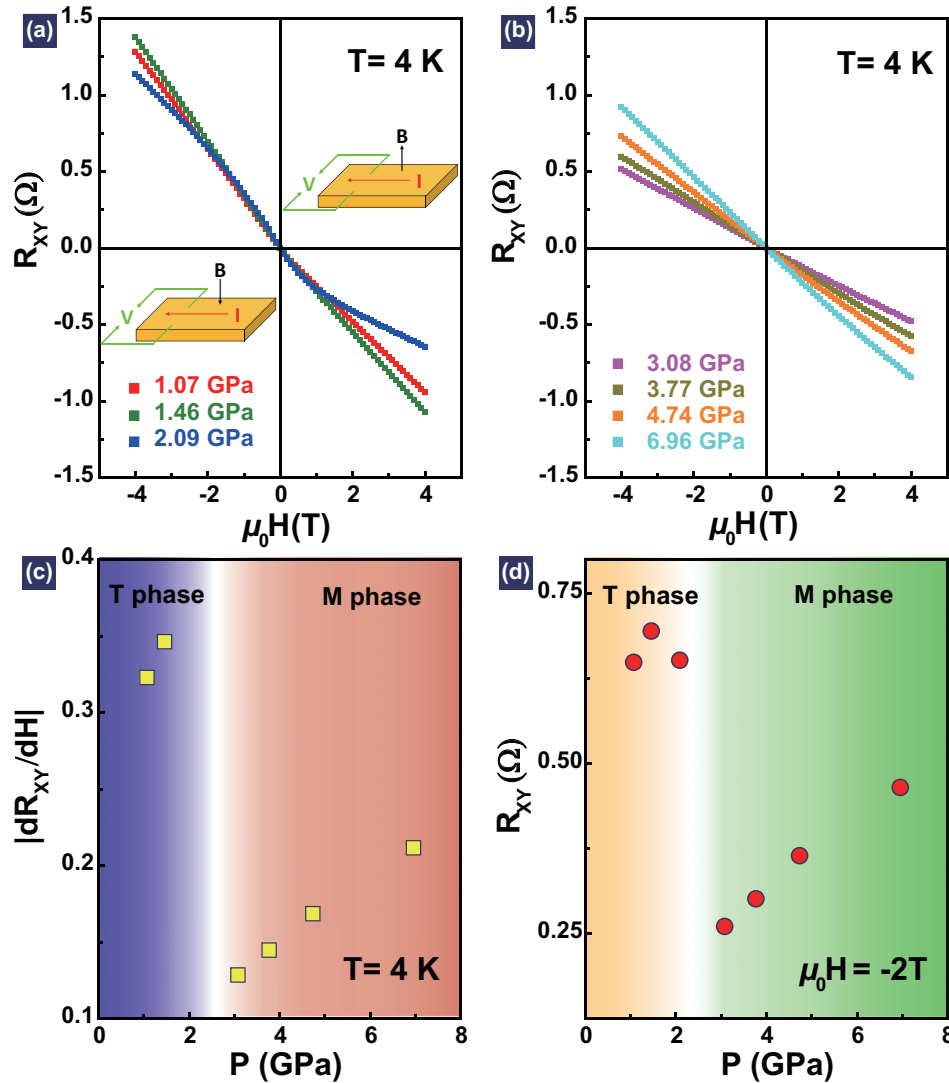


FIG. 3. (Color online) (a),(b) Hall resistance (R_{XY}) as a function of magnetic field for single-crystal Cd_3As_2 at different pressures. (c),(d) dR_{XY}/dH and R_{XY} as a function of pressure, showing the dramatic drop in dR_{XY}/dH and R_{XY} (at a field of 2 T) at 4 K near the transition from the Dirac semimetal to high-pressure semiconducting phase.

destabilizes the metallic behavior of Cd_3As_2 , converting the sample from its ambient pressure metallic behavior to semiconducting behavior between 2.45 and 3.99 GPa [Fig. 2(a)]. The change from metallic to semiconducting state lies in the pressure range of the T - M phase transition. On further increasing pressure, the semiconducting behavior becomes pronounced [Fig. 2(b)]. We estimate the activation energy gap (ε_A) for the excitation of charge carriers as a function of pressure, on the basis of the Arrhenius equation $\rho \sim \exp(\varepsilon_A/2k_B T)$ [inset of Fig. 2(b)]. The ε_A opens at 3.99 GPa ($\varepsilon_A = 13.5$ meV) in the M phase and increases rapidly with pressure. This phenomenon is in stark contrast to the common picture that pressure usually drives an insulator (or semiconductor) into a metal due to the band broadening, which leads us to expect that the semimetal Cd_3As_2 , after undergoing a structure phase transition under pressure, will be more metallic. This unusual pressure effect on Cd_3As_2 demonstrates the uncommon characteristic of its electron structure, which should be stemmed from its unique topological semimetal state protected by CRS. The gap opening found in this study gives strong support for the position that the pressure-induced change of CRS splits the bulk 3D Dirac points at the Fermi level, namely the breakdown of the 3DDSM state.

We measured the Hall resistance (R_{XY}) as a function of magnetic field at 4 K under pressure. Figures 3(a) and 3(b) show the overall features of the R_{XY} measured on the Cd_3As_2 single crystal in the field to 4 T for various pressures. We find that R_{XY} against magnetic field displays linear behavior both in its T phase [12–14] and M phase. However, the R_{XY} - H curve takes on two distinct slopes: a large slope for the T phase and a small slope for the M phase [Fig. 3(c)]. Around the phase transition, the dR_{XY}/dH drops by about 60%. The switch in Hall resistance slope supports the conclusion that the 3DDSM state of Cd_3As_2 is destroyed with pressure because the change of dR_{XY}/dH corresponds to a change of band structure [40]. The pressure dependence of R_{XY} is plotted in Fig. 3(d), which clearly illustrates the remarkable difference of Hall resistance before and after the transition. The R_{XY} of the pressurized Cd_3As_2 drops by more than a factor of 3 when it turns into the high-pressure semiconducting phase. These data are the supporting evidence for breakdown of the 3DDSM state in pressurized Cd_3As_2 . Intriguingly, the R_{XY} measured at 2.09 GPa shows kinks in both the positive and the negative directions of the magnetic field [Fig. 3(a)], a possible indication of the presence of an intermediate electronic state that may be of significant interest for further study.

It has been shown that one of the striking features of the 3DDSM is that the electron mobility is very high by virtue of 3D massless Dirac or Weyl fermions [12–18]. Experimentally, the best way to identify the breakdown of the 3DDSM state under pressure is to measure the pressure dependence of the electron mobility. A remarkable drop in mobility should be observed when the 3DDSM state is destroyed. To further clarify this issue, we obtained the pressure-dependent electron mobility of Ca_3As_2 (Fig. 4). We find that the mobility (μ) of the sample in the tetragonal 3DDSM state has a relatively high value, in good agreement with the values reported in the literature [12,13,19,41], and is nearly pressure independent, revealing that the charge carriers in the pressure range from ambient pressure to 2.5 GPa are relatively massless. However,

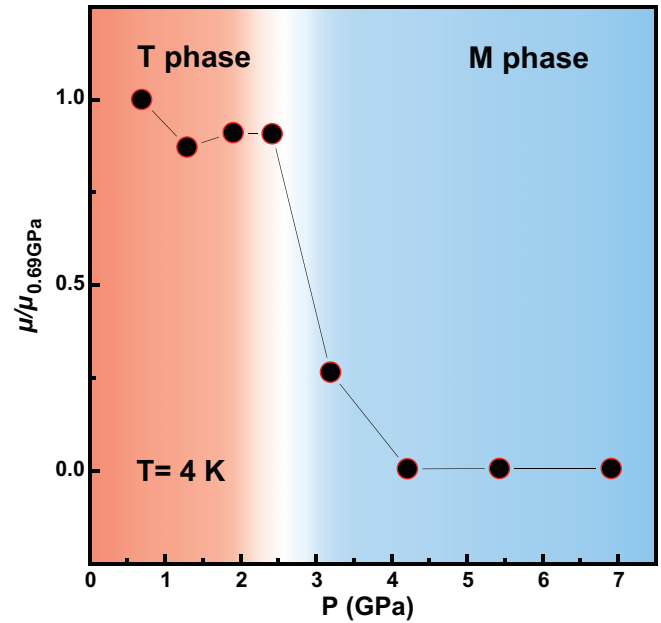


FIG. 4. (Color online) Pressure dependence of the electron mobility of single-crystal Cd_3As_2 at different temperatures. The data are derived from Hall measurements. The magnetic field is applied perpendicular to the (112) plane, and the current is applied in the (112) plane. The ambient-pressure electron mobility (μ) of the Cd_3As_2 sample employed is about 9.2×10^4 cm^2/Vs , in good agreement with values reported [12–18]. The normalized μ of pressurized Cd_3As_2 is derived from the equation of $\mu = R_H/\rho$, where R_H is the Hall coefficient and ρ is resistivity.

a dramatic reduction in electron mobility is found at pressures greater than 2.5 GPa; the mobility μ drops by about 74% at 3 GPa and by about 99% at 4 GPa. These results presented in Fig. 4 are the further evidence of the breakdown of the 3DDSM state in pressurized Cd_3As_2 .

In summary, we find experimental evidence for a pressure-induced breakdown of the 3DDSM state in Cd_3As_2 through *in situ* high-pressure x-ray diffraction and transport measurements. Our results demonstrate that external pressure leads Cd_3As_2 to undergo a crystal structure phase transition from a tetragonal phase in space group $I4_1/acd$ to a monoclinic phase in space group $P2_1/c$, which turns it from a Dirac semimetal into a semiconductor. This was characterized by the opening of an activation energy gap and substantial changes in the dR_{XY}/dH slope and electron mobility. Further study on the breakdown of the 3DDSM state in Cd_3As_2 under pressure will be of significant interest.

ACKNOWLEDGMENTS

The work in China was supported by the NSF of China (Grants No. 91321207 and No. 11427805), 973 projects (Grants No. 2011CBA00100 and No. 2010CB923000), and the Strategic Priority Research Program (B) of the Chinese Academy of Sciences (Grant No. XDB07020300). The work in the USA was supported by the ARO MURI on topological insulators, Grant No. W911NF-12-1-0461, and the US Department of Energy, Office of Science, Office of Basic Energy Sciences under Award No. DE-SC0011978.

- [1] Z. J. Wang, Y. Sun, X. Q. Chen, C. Franchini, G. Xu, H. M. Weng, X. Dai, and Z. Fang, *Phys. Rev. B* **85**, 195320 (2012).
- [2] Z. J. Wang, H. M. Weng, Q. S. Wu, X. Dai, and Z. Fang, *Phys. Rev. B* **88**, 125427 (2013).
- [3] M. Z. Hasan and J. E. Moore, *Annu. Rev. Condens. Matter Phys.* **2**, 55 (2011).
- [4] S. M. Young, S. Zaheer, J. C. Y. Teo, C. L. Kane, E. J. Mele, and A. M. Rappe, *Phys. Rev. Lett.* **108**, 140405 (2012).
- [5] Z. K. Liu, B. Zhou, Z. J. Wang, H. M. Weng, D. Prabhakaran, S.-K. Mo, Y. Zhang, Z. X. Shen, Z. Fang, X. Dai, Z. Hussain, and Y. L. Chen, *Science* **343**, 864 (2014).
- [6] S.-Y. Xu, C. Liu, S. K. Kushwaha, T.-R. Chang, J. W. Krizan, R. Sankar, C. M. Polley, J. Adell, T. Balasubramanian, K. Miyamoto, N. Alidoust, G. Bian, M. Neupane, I. Belopolski, H.-T. Jeng, C.-Y. Huang, W.-F. Tsai, H. Lin, F. C. Chou, T. Okuda *et al.*, [arXiv:1312.7624](https://arxiv.org/abs/1312.7624).
- [7] Z. K. Liu, J. Jiang, B. Zhou, Z. J. Wang, Y. Zhang, H. M. Weng, D. Prabhakaran, S.-K. Mo, H. Peng, P. Dudin, T. Kim, M. Hoesch, Z. Fang, X. Dai, Z. X. Shen, D. L. Feng, Z. Hussain, and Y. L. Chen, *Nat. Mater.* **13**, 677 (2014).
- [8] M. Neupane, S.-Y. Xu, R. Sankar, N. Alidoust, G. Bian, C. Liu, I. Belopolski, T.-R. Chang, H.-T. Jeng, H. Lin, A. Bansil, F. C. Chou, and M. Z. Hasan, *Nat. Commun.* **5**, 3786 (2014).
- [9] S. Borisenko, Q. Gibson, D. Evtushinsky, V. Zabolotnyy, B. Büchner, and R. J. Cava, *Phys. Rev. Lett.* **113**, 027603 (2014).
- [10] H. M. Yi, Z. J. Wang, C. Y. Chen, Y. G. Shi, Y. Feng, A. J. Liang, Z. J. Xie, S. L. He, J. F. He, Y. Y. Peng, X. Liu, Y. Liu, L. Zhao, G. D. Liu, X. L. Dong, J. Zhang, M. Nakatake, M. Arita, K. Shimada, H. Namatame *et al.*, *Sci. Rep.* **4**, 6106 (2014).
- [11] S. Jeon, B. B. Zhou, A. Gyenis, B. E. Feldman, I. Kimchi, A. C. Potter, Q. D. Gibson, R. J. Cava, A. Vishwanath, and A. Yazdani, *Nat. Mater.* **13**, 851 (2014).
- [12] T. Liang, Q. Gibson, M. N. Ali, M. H. Liu, R. J. Cava, and N. P. Ong, *Nat. Mater.* **14**, 280 (2015).
- [13] L. P. He, X. C. Hong, J. K. Dong, J. Pan, Z. Zhang, J. Zhang, and S. Y. Li, *Phys. Rev. Lett.* **113**, 246402 (2014).
- [14] J. Y. Feng, Y. Pang, D. S. Wu, Z. J. Wang, H. M. Weng, J. Q. Li, X. Dai, Z. Fang, Y. G. Shi, and L. Lu, [arXiv:1405.6611](https://arxiv.org/abs/1405.6611).
- [15] Y. F. Zhao, H. W. Liu, C. L. Zhang, H. C. Wang, J. F. Wang, Z. Q. Lin, Y. Xing, H. Lu, J. Liu, Y. Wang, S. Jia, X. C. Xie, and J. Wang, [arXiv:1412.0330](https://arxiv.org/abs/1412.0330).
- [16] A. Narayanan, M. D. Watson, S. F. Blake, N. Bruyant, L. Drigo, Y. L. Chen, D. Prabhakaran, B. Yan, C. Felser, T. Kong, P. C. Canfield, and A. I. Coldea, *Phys. Rev. Lett.* **114**, 117201 (2015).
- [17] J. Z. Cao, S. H. Liang, C. Zhang, Y. W. Liu, J. W. Huang, Z. Jin, Z. G. Chen, Z. J. Wang, Q. S. Wang, J. Zhao, S. Y. Li, X. Dai, J. Zou, Z. C. Xia, L. Li, and F. X. Xiu, [arXiv:1412.0824](https://arxiv.org/abs/1412.0824).
- [18] S. E. R. Hiscocks and C. T. Elliott, *J. Mater. Sci.* **4**, 784 (1969).
- [19] L. G. Caron, J.-P. Jay-Gerin, and M. J. Aubin, *Phys. Rev. B* **15**, 3879 (1977).
- [20] K. C. Saraswat, C. O. Chui, D. Kim, T. Krishnamohan, and A. Pethe, *Proceedings of Electron Devices Meeting (IEDM), 2006* (IEEE, Piscataway, 2006), pp. 1–4.
- [21] C. C. Stoumpos, C. D. Malliakas, and M. G. Kanatzidis, *Inorg. Chem.* **52**, 9019 (2013).
- [22] L. Fu, C. L. Kane, and E. J. Mele, *Phys. Rev. Lett.* **98**, 106803 (2007).
- [23] D. Hsieh, D. Qian, L. Wray, Y. Xia, Y. S. Hor, R. J. Cava, and M. Z. Hasan, *Nature* **452**, 970 (2008).
- [24] M. Z. Hasan and C. L. Kane, *Rev. Mod. Phys.* **82**, 3045 (2010).
- [25] X. L. Qi and S. C. Zhang, *Rev. Mod. Phys.* **83**, 1057 (2011).
- [26] M. Dzero, K. Sun, V. Galitski, and P. Coleman, *Phys. Rev. Lett.* **104**, 106408 (2010).
- [27] B. J. Yang and N. Nagaosa, *Nat. Commun.* **5**, 4898 (2014).
- [28] A. A. Burkov, M. D. Hook, and L. Balents, *Phys. Rev. B* **84**, 235126 (2011).
- [29] G. B. Halász and L. Balents, *Phys. Rev. B* **85**, 035103 (2012).
- [30] L. A. Wray, S.-Y. Xu, Y. Q. Xia, D. Hsieh, A. V. Fedorov, Y. S. Hor, R. J. Cava, A. Bansil, H. Lin, and M. Z. Hasan, *Nat. Phys.* **7**, 32 (2011).
- [31] W. Witczak-Krempa, G. Chen, Y. B. Kim, and L. Balents, *Annu. Rev. Condens. Matter Phys.* **5**, 57 (2014).
- [32] X. G. Wan, A. M. Turner, A. Vishwanath, and S. Y. Savrasov, *Phys. Rev. B* **83**, 205101 (2011).
- [33] M. N. Ali, Q. Gibson, S. Jeon, B. B. Zhou, A. Yazdani, and R. J. Cava, *Inorg. Chem.* **53**, 4062 (2014).
- [34] A. Eichler and W. Gey, *Rev. Sci. Instrum.* **50**, 1445 (1979).
- [35] V. A. Sidorov, E. D. Bauer, N. A. Frederick, J. R. Jeffries, S. Nakatsuji, N. O. Moreno, J. D. Thompson, M. B. Maple, and Z. Fisk, *Phys. Rev. B* **67**, 224419 (2003).
- [36] H. K. Mao, J. Xu, and P. M. Bell, *J. Geophys. Res.* **91**, 4673 (1986).
- [37] M. D. Banus and Mary C. Lavine, *High Temperatures - High Pressures* **1**, 269 (1969).
- [38] C. W. F. T. Pistorius, *High Temperatures - High Pressures* **7**, 441 (1975).
- [39] See Supplemental Material at <http://link.aps.org/supplemental/10.1103/PhysRevB.91.165133> for Breakdown of Three-dimensional Dirac Semimetal State in pressurized Cd₃As₂.
- [40] X. Zhang, L. Yu, S. von Molnár, Z. Fisk, and P. Xiong, *Phys. Rev. Lett.* **103**, 106602 (2009).
- [41] J. Cisowski and W. Żdanowicz, *Acta Phys. Pol. A* **43**, 295 (1973).
- [42] A. de Combarieu and J.-P. Jay-Gerin, *Phys. Rev. B* **25**, 2923 (1982).